



UNIVERSITI PUTRA MALAYSIA

**EFFECT OF PROCESSING PARAMETERS ON THE PHYSICAL
CHARACTERISTICS OF PALM OIL-BASED TABLE MARGARINE**

MISKANDAR MAT SAHRI

FSMB 2002 21

**EFFECT OF PROCESSING PARAMETERS ON THE PHYSICAL
CHARACTERISTICS OF PALM OIL-BASED TABLE MARGARINE**

By

MISKANDAR MAT SAHRI

**Thesis Submitted to the School of Graduate Studies, Universiti Putra Malaysia,
In Fulfilment of the Requirements for the Degree of Master of Science**

June 2002



DEDICATION

Especially dedicated to my beloved wife Hanirah
and children
Hajar Marhamah, Muhammad Hanif, Hayati Munirah, Hanis Muslimah, Muhammad
Halim and Muhammad Azim

Abstract of thesis presented to the Senate of Universiti Putra Malaysia in fulfilment
of the requirements for the Degree of Master of Science

**EFFECT OF PROCESSING PARAMETERS ON THE PHYSICAL
CHARACTERISTICS OF PALM OIL-BASED TABLE MARGARINE**

By

MISKANDAR MAT SAHRI

June 2002

Chairman: Professor Yaakob Bin Che Man, Ph.D.

Faculty: Food Science and Biotechnology

The optimum processing conditions are as important as the product formulation in margarine production. However, the effects of the processing parameters, especially the emulsion temperature, flow rate, product temperature and pin-worker speed, have not yet been thoroughly investigated. This study, using a scraped-surface tube cooler pilot plant, investigated the effects of these parameters on a palm oil-based margarine during its processing and storage.

The processing conditions mainly affected the margarine through its consistency by influencing the solid fat content (SFC) and the crystal polymorph formed. At temperatures of 40°C, 45°C and 50°C, there was no SFC in the

emulsions, but 15.9%, 13.9% and 15.6% were formed in the tube cooler, respectively. The emulsion temperature had no significant effect on the product during storage, although some differences were observed during processing. A margarine with stable consistency and SFC, a moderately high softening point and in the β' polymorph was formed from the emulsion at 45°C. The margarine consistency was the highest at 15 kg/hr emulsion flow rate, and the lowest at 45 kg/hr. Margarine processed at tube cooler temperature 25°C produced an unusual hardening with formation of the β -crystal polymorph in the second week of storage. At 15°C and 20°C it remained in the β' -crystal form for four and three weeks, respectively. The SFCs developed in the tube cooler at the pin-worker speeds of 100 and 300 RPM were 9.12% and 10.11%, respectively. The higher speed retained the emulsion longer in the tube cooler, allowing more crystal formation. The SFCs after the pin-worker at 100 and 300 RPM were 9.01% and 8.72%, respectively. The higher speed severely destroyed the crystal structure, lowering the SFC. The consistency of the margarines at the pin-worker speeds of 100, 200 and 300 RPM were 214, 210.4 and 204 g/cm², respectively. They were already in a mixture of β' and β crystal forms in the first week after production.

The study suggests that margarine manufacturers using 100% palm oil should use an emulsion temperature of 45°C, emulsion flow rate at 100% of the plant capacity, pin-worker speed of 200 RPM and chilling temperature of the scraped surface tube cooler of 20°C.

Abstrak tesis yang dikemukakan kepada Senat Universiti Putra Malaysia sebagai memenuhi keperluan untuk Ijazah Master Sains

**KESAN PARAMETER PEMROSESAN TERHADAP SIFAT FIZIKAL
MARJERIN BERASASKAN MINYAK SAWIT**

Oleh

MISKANDAR MAT SAHRI

Jun 2002

Pengerusi: Profesor Yaakob Bin Che Man, Ph.D.

Fakulti: Sains Makanan dan Bioteknologi

Keberkesanan parameter pemerosesan dan pemilihan formulasi adalah sama pentingnya bagi penghasilan marjerin yang bermutu. Walau bagaimanapun, keberkesanan pemerosesan marjerin dari minyak sawit khususnya, pengemulsian, aliran emulsi, suhu tiub penyejukan dan kelajuan pin-pengaduk belum dikaji secara terperinci. Kajian ini yang menggunakan peralatan tersebut telah mengenalpasti kesan aruhnya terhadap produk semasa pemerosesan dan penstoran.

Kaedah pemerosesan mempengaruhi kekonsistenan marjerin dengan mengubah kandungan pepejal lemak (KPL) dan hablur polimorfnya. Suhu

pengemulsian tiada kesan ketara terhadap produk semasa penstoran, walaupun perubahan produk dapat dikesan semasa pemerosesan. Pada suhu pengemulsian 40, 45 dan 50°C, KPL tidak dapat dikesan pada suhu-suhu tersebut, tetapi KPL masing-masing meningkat ke 15.9%, 13.9% dan 15.6% di dalam tiub penyejukan. Marjerin terbaik yang dihasilkan telah diemulsikan pada suhu 45°C, mempunyai kekonsistenan dan nilai pelembutan yang sederhana dan berada pada hablur jenis β' . Pada kelajuan aliran emulsi 15kg/j marjerin yang dihasilkan adalah tinggi kekonsistennya, berbanding 45kg/j yang rendah. Marjerin yang diproses pada suhu tiub penyejukan 25°C mengalami kekerasan luar biasa seawal minggu kedua dengan pembentukan hablur β . Walau bagaimanapun pada suhu pemerosesan 20 dan 15°C, kekonsistenan dan nilai pelembutan marjerin adalah seragam, manakala hablur adalah dalam β' sehingga minggu ketiga dan keempat. KPL yang terbentuk di dalam tiub penyejukan oleh kelajuan pin-pengaduk 100 RPM ialah 9.12% manakala oleh kelajuan 300 RPM ialah 10.11%, menunjukkan bahawa kelajuan pin pengaduk telah memperlahankan aliran produk di dalam tiub penyejukan dan meningkatkan penghabluran. KPL selepas melalui pin pengaduk pula adalah 8.72% pada kelajuan 300 RPM dan 9.01% pada 100 RPM, menunjukkan bahawa pemusnahan ikatan hablur telah berlaku semasa pengadukan. Semasa penstoran, kekonsistenan marjerin daripada kelajuan pin pengadukan 100 RPM ialah 214 g/cm², 300 RPM ialah 210.4 g/cm² dan 200 RPM ialah 204 g/cm², manakala hablur yang terbentuk ialah campuran diantara β' dan β pada seawal minggu pertama

Kajian yang dijalankan telah mendapati bahawa bagi penghasilan marjerin yang terbaik daripada minyak sawit 100% pengilang seharusnya menggunakan suhu pengemulsian 45°C, kelajuan emulsi pada kadar 100% kapasiti mesin, suhu tiub penyejukan 20°C dan kelajuan pin pengaduk 200 RPM.

ACKNOWLEDGEMENTS

I would like to express my sincere gratitude to Professor Dr. Yaakob Bin Che Man, the chairman of my Supervisory Committee for his kind assistance, advice and encouragement during the preparation of this thesis. I am so grateful to the other members of the Supervisory Committee, Associate Professor Dr. Russly Bin Abd. Rahman and Dr. Mohd Suria Affandi Bin Yusoff of MPOB, for their guidance, support and comments.

I would like to acknowledge Malaysian Palm Oil Board for the permission given to me to complete this Master Degree program, support on the research material and equipment. I would like to acknowledge the staff in the Oil and Fat Technology Centre, Malaysian Palm Oil Board namely En Radzuan Hussein, En Suid Aziz, En Ahmad Hisham for their assistance during my work on Gerstennberg and Agger Perfector Plant, Cik Ramlah Ahmad who had assisted me during my work on Nuclear Magnetic Resonance and Che Zulkarinah Kamaruddin for assisting me during my work on x-ray diffractometer.

Last but not least, I would like to express my heartiest appreciation to my beloved wife Hanirah Hassan and children for their moral encouragement, patience and understanding throughout my studies.




I certify that an Examination Committee met on 11th June 2002 to conduct the final examination of Miskandar Mat Sahri on his Master of Science thesis entitled “Effect of Processing Parameters on the Physical Characteristics of Palm Oil-Based Table Margarine” in accordance with Universiti Pertanian Malaysia (Higher Degree) Act 1980 and Universiti Pertanian Malaysia (Higher Degree) Regulations 1981. The Committee recommends that the candidate be awarded the relevant degree. Members of the Examination Committee are as follows:

Hasanah Mohd Ghazali, Ph.D.
Professor
Faculty of Food Science and Biotechnology
Universiti Putra Malaysia
(Chairperson)

Yaakob Che Man, Ph.D.
Professor
Faculty of Food Science and Biotechnology
Universiti Putra Malaysia
(Member)

Mohd. Suria Affandi Yusoff, Ph.D.
Principal Research Officer
Malaysian Palm Oil Board
(Member)

Russly Abd Rahman, Ph.D.
Associate Professor
Faculty of Food Science and Biotechnology
Universiti Putra Malaysia
(Member)

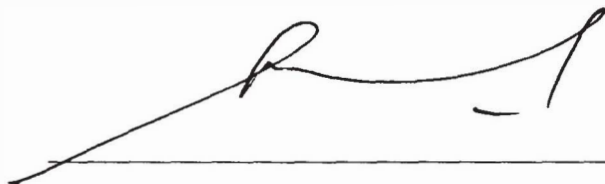

SHAMSHER MOHAMAD RAMADILI, Ph.D.
Professor /Deputy Dean,
School of Graduate Studies
Universiti Putra Malaysia

Date: 24 JUL 2002

This thesis submitted to the Senate of Universiti Putra Malaysia has been accepted as fulfilment of the requirements for the degree of Master of Science



AINI IDERIS, Ph.D.
Professor / Dean
School of Graduate Studies,
Universiti Putra Malaysia.

Date: **12 SEP 2002**

DECLARATION

I hereby declare that the thesis is based on my original work except for quotations and citations which have been duly acknowledged. I also declare that it has not been previously or currently submitted for any other degree at UPM or other institutions.



Miskandar Mat Sahri

Date: 23 Julai, 2002

TABLE OF CONTENTS

	Page
ABSTRACT	iii
ABSTRAK	v
ACKNOWLEDGEMENTS	viii
APPROVAL	ix
DECLARATION	xi
LIST OF TABLES	xv
LIST FIGURES	xviii
LIST OF PLATES	xix
LIST OF ABBREVIATIONS	xx
 CHAPTER	
I GENERAL INTRODUCTION	1
 II LITERATURE REVIEW	4
Margarine.....	4
Characteristics of Margarines.....	5
Recent Development in Margarine	
Formulation.....	9
Ingredients Affecting the Production and Properties of	
Margarines.....	12
Oils and Fats.....	12
Water or Milk.....	30
Emulsifiers.....	31
Ingredients Affecting Sensory Properties and Shelf Life of	
Margarine.....	35
Salt.....	35
Antioxidants.....	35
Preservatives.....	36
Flavouring Agent.....	37
Vitamins.....	38
Colouring Agent.....	38
Food Grade Oil Preparation by Refining.....	39



	Modification Processes of Oils and Fats for Margarine	
	Production.....	42
	Fractionation.....	42
	Blending.....	43
	Hydrogenation.....	45
	Interesterification.....	49
	Development of Margarine Processing Technology.....	50
	Effect of Processing on the Physical Properties of	
	Margarine.....	51
	Effect of Emulsification.....	52
	Effect of Feeding Pump Speed.....	54
	Effect of Cooling Temperature.....	56
	Effect of Working	60
	Effect of Resting.....	62
	Effect of Tempering.....	63
	Product Characteristics and Analyses.....	63
	Spreadability	64
	Consistency and Texture.....	65
	Oil Separation.....	68
	Polymorphic form and Sandiness.....	69
III	MATERIALS AND METHODS.....	71
	Materials.....	71
	Methods.....	71
	Production of Margarine.....	71
	Experimental Design.....	74
	Sampling	74
	Physical Analyses.....	75
	Quality Assessment.....	76
	Data Analysis.....	77
IV	RESULTS AND DISCUSSION	78
	i) Effect of Emulsion Temperatures on The Physical	
	Properties of Palm Oil-Based Table Margarine.....	78
	Changes in Product Properties during Processing.....	80
	Development of SFC during Storage.....	84
	Consistency of Margarine during Storage.....	85
	Polymorphic Transformation during Storage	88
	Changes in Softening Point during Storage.....	88
	Summary.....	89
	ii) Effect of Emulsion Flow Rate on the Physical Properties	
	of Palm Oil-Based Table Margarine.....	90

Development of SFC during Processing.....	91
Consistency of Margarine Processed by Different Flow rates during Storage.....	94
SFC Developed by the Different Margarines during Storage.....	95
Polymorphic Changes during Storage.....	96
Summary.....	98
 iii) Effect of Scrape-Surface Tube Cooler Temperature on the Physical Properties of Palm Oil-Based Table Margarine.....	99
SFCs of Emulsions at Different Tube cooler Temperatures.....	100
Development of SFC in Margarines Made at Different Tube cooler Temperatures during Storage.....	103
Effect of Tube cooler Temperatures on the Consistency of Margarine.....	105
Different Crystal Formation during Storage.....	106
Summary.....	109
 iv) Effect of Pin-Worker Speed on the Physical Properties of Palm Oil-Based Table Margarine.....	110
SFCs of Margarines Processed at Different Pin- worker Speeds.....	111
Effect of Pin-Worker Speed on SFC during Storage.....	113
Influence of Pin-Worker Speed on the Consistency of Margarine during Storage.....	114
Polymorphic Changes during Storage.....	117
Summary.....	119
 V CONCLUSION AND RECOMMENDATION.....	120
 BIBLIOGRAPHY.....	121
 APPENDICES.....	130
 BIOGRAPHICAL SKETCH.....	136

LIST OF TABLES

Table		Page
1	Types and packaging of margarine	5
2	Some margarine formulations for baking and their SFCs.....	7
3	The Properties of the different polymorphs.....	16
4	Crystal polymorphic tendency of selected oils And fats.....	17
5	Stable polymorphs of fatty acid positional distribution in selected TAGs.....	19
6	Fatty acid Composition of important edible oils.....	20
7	The contribution of TAG carbon numbers to the formation of β' and β crystal in margarine	21
8	Crystal polymorphs contributed by major TAGs in Palm Oil.....	21
9	SMPs of some fatty acid common in oils and fats.....	25
10	HLB values of some emulsifiers.....	33
11	Selected oils and fats categorized by their SMP.....	43
12	Effect of emulsion holding temperature (point X) on sample temperatures at Points Y and Z (Figure 7).....	80
13	SFCs of palm oil margarines processed at different emulsion temperatures at 28°C.....	84
14	Penetration yields (consistency) (g/cm^2) of palm oil margarine processed under different emulsion temperatures.....	85

15	Polymorphic transformation of palm oil margarines made from different emulsion temperatures during storage at 28°C.....	87
16	Softening point of palm oil margarines processed under different emulsion temperatures	89
17	The SFCs developed by different processing flow rates at different sampling points.....	91
18	Product temperatures at the various sampling points during production at different flow rates.....	92
19	Penetration yields (g/cm ²) during storage of palm oil margarine at different flow rates	94
20	Development of SFC in palm oil margarines from different flow rates during storage.....	96
21	Polymorphic transformation of palm oil margarines processed at different flow rate during storage	97
22	SFCs of palm oil margarines processed at different tube cooler temperatures and stored at 28°C.....	104
23	Penetration yields (consistency) (g/cm ²) of palm oil margarine processed at three tube cooler temperatures and stored at 28°C	105
24	Polymorphic transformation of palm oil margarines processed at different tube cooler temperatures and stored at 28°C	107
25	Product temperatures (°C) at different sampling points in margarine processing	111
26	Development of isothermal SFC at different sampling points in margarine production	112
27	Sacs of palm oil-based table margarines as affected by pin-worker speeds.....	114

28	Polymorphic transformation of palm oil margarines at different pin-worker speeds	118
29	Triglycerides composition of palm oil and palm kernel oil fractions.....	130
30	SFC of palm oil and palm kernel oil fractions.....	130

LIST OF FIGURES

Figure	Page
1 Crystal arrangement	16
2 Typical SFC profile of different types of margarines.....	29
3 Emulsion of water-in-oil.....	31
4 SFC versus temperature showing a steep slope of a selectively hydrogenated and gradual slope of non- selectively hydrogenated oil.....	48
5 Cross section of tube cooler showing the knife scraper and the annular space.....	59
6 Relationship between SFC and yield value in margarine.....	67
7 Schematic diagram of margarine processing showing the perfector units and the various sampling points	72
8 SFC developed at sampling Points Y and Z during processing at different emulsion temperatures	81
9 SFC (%) at the exits of tube cooler (Y) and pin-worker (Z) in the production of margarine and the SFC of palm oil.	101
10 Consistency of palm oil margarines (g/cm^2) at different pin-worker speeds during storage at 28°C	115

LIST OF PLATES

Plate		Page
A	Model of hydrogenation process of a vegetable oil.....	131
B	Flowchart of margarine production	134
C	Analysis of margarine samples.....	135

LIST OF ABBREVIATION

Abbreviation

AOCS	American oil chemists' society
C	Caproic acid
CAN	Canola
CB	Cocoa butter oil
CNO	Coconut oil
CSO	Cottonseed oil
E	Elaidic acid
FAC	Fatty acid composition
GNO	Ground nut oil
Ln	Linoleic acid
L	Lauric acid
LAR	Lard
LL	Linolenic acid
M	Myristic acid
MDP	Mettler dropping point
MF	Milk fat
MPOB	Malaysian Palm Oil Board
MSP	Mettler softening point
MZO	Corn oil/ maize oil

NMR	Nuclear magnetic resonance
O	Oleic acid
OL	Olive oil
P	Palmitic acid
PKO	Palm kernel oil
PKOo	Palm kernel olein
PO	Palm oil
Poo	Palm olein
Pos	Palm Stearin
RBD	Refined bleached and deodorized
RBO	Rice bran oil
RPM	Rotation per minute
SAF	Safflower oil
SBO	Soybean oil
SES	Sesame oil
SFC	Solid fat content
SFO	Sunflower oil
SMP	Slip melting point
St	Stearic acid
TAG	Triacylglycerol
TAL	Tallow

CHAPTER I

GENERAL INTRODUCTION

The properties of a margarine can be varied for its intended use. The layman differentiates between margarines by simple sensory evaluation and common adjectives to describe the product are *soft, smooth, hard, brittle, yellowish, whitish, salty, oily* and *buttery*. Manufacturers also consider the properties of their margarine when packaging them for both storage and their intended use – in packets, tubs, tins and cartons - depending on whether they are for households, industrial use, institutional catering or repacking. The range of products can be grouped by their properties - baking index, creaming index, yield value, hardness index, texture and polymorphic crystal structure - for ease of use (Podmore, 1994; Haighton, 1965; deMan *et al.*, 1989a; Greenwell, 1981). However, to conform to the requirements on the properties of their products, manufacturers have to select the correct types of oils and fats for their formulations, as well as the processing conditions and temperature for storage.

Price, characteristics and availability are some of the factors considered when selecting oils for margarine production. Soybean oil, sunflower oil, palm oil, canola, coconut oil and palm kernel oil are some of the most commonly used oils (Moore, 1971). Soybean oil is mainly produced in the U.S.A., sunflower oil in Europe, palm oil and palm kernel oil in Malaysia and canola in Canada. In 2000, Malaysia produced

12 million tonnes of palm oil and exported 9.08 million tonnes (Mohd Nasir and Hasiah, 2001).

The use of palm oil can be traced back some 5,000 years (Berger, 1994). However, its substantive use and trade started only in 1960. Since then it has been gaining market share year by year (Berger, 1994; Mohd Nasir and Hasiah, 2001). Considerable research has been done on palm oil, especially in nutrition, food products, processing, oleochemicals and animal feed. It is increasingly being used mixed with the more liquid oils because of the desirable crystallization properties it imparts to margarines and shortenings. This is in stark contrast to the early days when palm oil was perceived as an inferior oil for margarine (Madsen, 1971). Indeed, unbeknown to many, several palm products, like palm olein and palm stearin, have crept into various foods.

However, palm oil is not without its problems. Its slow crystallization makes it rather difficult to use in products like shortening and margarine (Gutcho, 1979; Duns, 1985) despite some good properties imparted. And despite the considerable work done, the problem has not yet been sufficiently addressed for the oil to compete and substitute fully for the hydrogenated liquid oils often used in margarines and shortenings. Further, very little is being done on the characteristics of the oil in influencing the margarine qualities. For example, in processing, deMan and deMan (1994) stated that formulations with the same solid fat content (SFC) need not necessarily produce margarines of the same quality. The product end point and

processing technique are still considered an art and kept secret by most companies although, doubtless, all will be known in time (Bernadini, 1983).

A proper guide on the effects of processing conditions and formulations on the product quality will be immensely useful to the industry and will broaden its scope for innovation. The ready availability of palm oil in the market will make the products made from it less expensive and more competitive with no quality problem such as oiling off, greasiness and sandiness.

The study was undertaken to determine the effects of various processing conditions on the physical properties of palm oil-based table margarine. The conditions investigated were:

- I. Emulsion temperature;
- II. Emulsion flow-rate;
- III. Tube cooler temperature; and
- IV. Pin-roller speed.

Special emphasis was placed on the development of crystal structure in processing and during storage.